

Systematic Study of Magnetic Interactions in Insulating Cuprates

Yoshiaki Mizuno, Takami Tohyama and Sadamichi Maekawa^a

^aInstitute for Materials Research, Tohoku University, Sendai 980-8577, Japan.

The magnetic interactions in one-dimensional, two-dimensional (2D) and ladder cuprates are evaluated systematically by using small Cu-O clusters. We find that the superexchange interaction J between nearest neighbor Cu spins strongly depends on Cu-O structure through the Madelung potential, and in 2D and ladder cuprates there is a four-spin interaction J_{cyc} , with magnitude of 10 % of J . We show that J_{cyc} has a strong influence on the magnetic excitation in the high-energy region of 2D cuprates.

A variety of insulating cuprates affords us an opportunity to study the magnetic properties of low-dimensional systems. Recent experiments for insulating cuprates have revealed interesting characteristics of magnetic interactions: The superexchange interaction between nearest neighbor Cu spins J remarkably depends on Cu-O network structure [1], and additional interactions such as a four-spin (4S) interaction are important for ladder [2] and two-dimensional (2D) cuprates [3]. These characteristics indicate the necessity to establish proper magnetic descriptions for the cuprates. In this paper we perform a systematic study of magnetic interactions for one-dimensional (1D), 2D, and ladder cuprates theoretically.

A starting model to describe the electronic states of cuprates is the d - p model, in which hopping integrals between Cu3d and O2p orbitals (T_{pd}) and between O2p orbitals (T_{pp}), an energy-level separation between the Cu3d and O2p orbitals (Δ), and Coulomb interactions on Cu and O sites are taken into account. T_{pd} and T_{pp} are obtained by considering not only the bond length dependence but also the effect of the Madelung potential around Cu and O ions. We find that the potential enhances the magnitudes of T_{pd} and T_{pp} in the 1D cuprates as compared with those in the 2D ones [1]. In the two-leg ladder compounds such as SrCu₂O₃, T_{pp} along the leg of the ladder is enhanced by the Madelung potential due to adjacent two-leg ladders. These enhancements play an important role in the dependence of J on the

dimensionality. The Δ is determined from the difference in the Madelung potential between Cu and O sites.

The magnetic interactions are evaluated by mapping the lowest several eigenstates of small clusters (Cu₂O₇, Cu₄O₁₂, and Cu₆O₁₇) for the d - p model onto those of the corresponding Heisenberg-type model [4]. For 2D systems, we take into account not only J , but also a diagonal interaction J_{diag} and 4S interaction J_{cyc} in the model: $H = J \sum_{\langle i,j \rangle} \mathbf{S}_i \cdot \mathbf{S}_j + J_{\text{diag}} \sum_{\langle\langle i,j \rangle\rangle} \mathbf{S}_i \cdot \mathbf{S}_j + J_{\text{cyc}} \sum_{\text{plaquette}} (P_{ijkl} + P_{ijkl}^{-1})$, where $\mathbf{S}_i$ is a spin operator at site i , and J_{cyc} is defined as the coefficient of the 4S cyclic permutation operators P_{ijkl} and P_{ijkl}^{-1} , which can be rewritten by using the two-spin interaction $(\mathbf{S}_i \cdot \mathbf{S}_j)$ and the four-spin interactions $(\mathbf{S}_i \cdot \mathbf{S}_j)(\mathbf{S}_k \cdot \mathbf{S}_l)$. For ladder systems, we distinguish between the nearest neighbor interactions along the leg (J_{leg}) and along the rung (J_{rung}) of the ladder.

The calculated results are summarized in Table 1, where we take La₂CuO₄, SrCu₂O₃, and Sr₂CuO₃ as typical systems of 2D, ladder and 1D cuprates, respectively (see Refs. 1 and 5 for the parameters used in the calculations). We find that J in the 1D cuprate is larger than that in the 2D one. This is caused by the enhancement of the hopping integrals in 1D cuprates as mentioned above. For 2D cuprates, we obtain J to be ~ 0.15 eV, consistent with the experimental values [1]. In addition, we find that J_{cyc} is 7 % of J , while J_{diag} is zero. These results are consistent with a previous cluster calculation [5], and a re-

Table 1

The magnetic interactions obtained by mapping the eigenstates of Cu_2O_7 , Cu_4O_{12} , and Cu_6O_{17} clusters for Sr_2CuO_3 , La_2CuO_4 , and SrCu_2O_3 , respectively, onto the corresponding Heisenberg-type models. The numbers in parentheses denote the deviation in the last significant digit.

Material	J [eV]	J_{diag} [eV]	J_{cyc} [eV]
Sr_2CuO_3	0.17	—	—
La_2CuO_4	0.146(1)	0.00(0)	0.011(1)
SrCu_2O_3	$J_{\text{leg}}: 0.195(5)$ $J_{\text{rung}}: 0.15(2)$	0.003(2)	0.018(2)

cent analysis of a multimagnon spectrum [3]. For ladder cuprates, we obtain $J_{\text{leg}}/J_{\text{rung}}=1.3$. The enhancement of T_{pp} along the leg of the ladder is the origin of the relation $J_{\text{leg}} > J_{\text{rung}}$. J_{cyc} is 10 % of J_{leg} . Note that the ratio $J_{\text{leg}}/J_{\text{rung}}$ is smaller than that believed so far, i.e., $J_{\text{leg}}/J_{\text{rung}} \sim 2$ [6]. However, the Heisenberg ladder with the present values of J_{leg} , J_{rung} , J_{cyc} and J_{diag} reproduces very well the experimental results of the temperature dependence of the magnetic susceptibility (not shown here). Therefore, we consider the values shown in Table 1 to be reasonable. Here we would like to emphasize that J_{cyc} plays a crucial role in obtaining the good agreement between the experimental and theoretical magnetic susceptibilities [4].

Next, in order to examine the effect of J_{cyc} on the magnetic excitation, we calculate the dynamical spin-correlation function $S(\mathbf{q}, \omega)$ for 2D cuprates. Figure 1 shows the dispersion and the intensity of $S(\mathbf{q}, \omega)$ for a 4×4 Heisenberg model with $J=0.146$ eV and $J_{\text{cyc}}=0.011$ eV. For comparison, the result for $J_{\text{cyc}}=0$ are also shown. We find that the intensity is not sensitive to J_{cyc} , while the dispersion is strongly suppressed in the high-energy region. In particular, it is worth noting that $\omega(\mathbf{q})$ at $\mathbf{q}=(\pi/2, \pi/2)$ becomes smaller than that at $\mathbf{q}=(\pi, 0)$. This is in contrast with the case of $J_{\text{cyc}}=0$, in which the magnetic zone boundary ($\mathbf{q}=(\pi, 0) \rightarrow (\pi/2, \pi/2)$) has a flat dispersion. Therefore, it is desirable that inelastic neutron-scattering experiments in the wide energy region

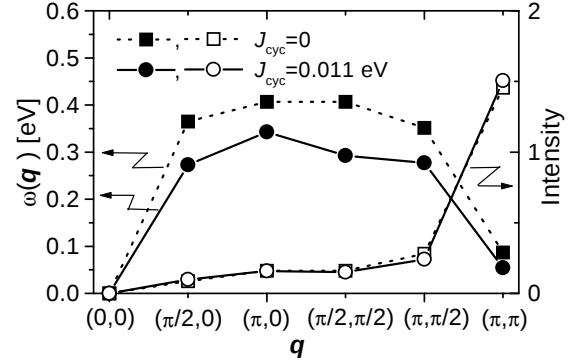


Figure 1. The magnetic excitation spectra of a 4×4 Heisenberg model with J and J_{cyc} .

be performed to verify the role of J_{cyc} , that is, the suppression of the dispersion at $(\pi/2, \pi/2)$.

In summary, we have evaluated the magnetic interactions in various cuprates systematically. We have shown that an ionic nature inherent in insulating cuprates is important for the material dependence of J . We found that J_{cyc} is ~ 10 % of J , and greatly influences the magnetic excitation spectra in 2D cuprates.

This work was supported by a Grant-in-Aid for Scientific Research on Priority Areas from the Ministry of Education, Science, Sports and Culture of Japan, CREST and NEDO. The parts of the numerical calculation were performed in the Supercomputer Center in ISSP, University of Tokyo, and the supercomputing facilities in IMR, Tohoku University.

REFERENCES

1. Y. Mizuno, T. Tohyama and S. Maekawa, Phys. Rev. B **58**, R14713 (1999).
2. M. Matsuda, K. Katsumata, R. S. Eccleston, S. Brehmer and H.-J. Mikeska, unpublished.
3. J. Lorenzana, J. Eroles and S. Sorella, Phys. Rev. Lett. **83**, 5122 (1999).
4. Y. Mizuno, T. Tohyama and S. Maekawa, J. Low Temp. Phys. **117** 389 (1999).
5. H. J. Schmidt and Y. Kuramoto, Physica C **167**, 263 (1990).
6. J.C. Johnston, Phys. Rev. B **54**, 13009 (1996).